

Evaluation of the Color Sorting Potential of a Clear PET Article with Label Coverage Greater than APR Design Guidance¹

Document Number: SORT-B-04

Publication or Revision Date: May 27, 2021

Introduction – Scope, significance and use - This test is one in the series of “Sorting Potential Test Methods” developed by the Association of Plastics Recyclers (APR).

The sorting potential test methods describe laboratory-scale representations of the most commonly used collection and Material Recovery Facility (MRF) processes for handling single-stream postconsumer recyclables. The test methods assume that these co-mingled recyclables are collected curbside, compacted in a typical recycling collection truck, transported to and processed through an automated MRF into bales of similar plastics, then further processed at the plastics reclaimer in their original form before being reduced in size.

These tests do not consider the plastics recycling process starting from or after size reduction at the plastics reclaimer. Nor do they represent other processes that may use different methods of collection and separation with different results. Furthermore, plastic sorting processes have some degree of variability in commercial practice. It is not the intent of this protocol to model every possible process outcome, but to choose a common set of parameters, widely employed, and which fall squarely within those used by industry.

The sorting potential tests are intended to identify specific design features that may cause an entire package to be lost in the recycling process. The consequences of a plastic article being mis-sorted prior to size reduction are more significant than in processes that follow size reduction since the entire package is lost to the plastics recycling stream rather than a mere component of the package. The modeling of sorting behavior in this test enables design engineers to focus their improvement efforts and is designed to complement the wide range of tests offered by APR that form the foundation of APR’s Design Guidance for plastic package recyclability.

Note: Many people recognize the optical bottle sorting process within MRF’s, however, US MRF’s don’t typically sort PET bottles by color. The color sorting process occurs at the PET recycler.

Typically, today’s PET reclaimers employ automated equipment that sorts plastic packaging and other items by color into three distinct groups: Clear + transparent light blue, transparent green, and other colors. For this equipment to operate effectively, it must accurately identify the color of the PET container beneath the label and direct it to the correct location. Otherwise, the article may be downgraded to a less valuable color stream. Large coverage labels can cause the article to be misdirected.

This specific Color Sorting Potential Test Method provides a means of evaluating whether a clear PET package that employs a label with a high surface area coverage can be accurately identified and sorted on pilot scale color sortation equipment that performs similarly to that used in production facilities. Good results in this

¹ Articles with label coverage greater than or equal to the following limits require testing: Container volume 550ml or less: 55%, Container volume > 550ml: 70%. Label coverage is defined by the label surface area divided by the article surface area, without including the neck finish or bottle base area.

benchmark test indicate that a plastic article has the potential to be sorted well in production conditions. Poor results indicate that an improvement in package or label design is desirable to promote recovery.

The test involves establishing the baseline performance of a commercial color auto-sorter that is located within a lab setting—adjusted as it would be at a PET recycler—by processing a known blend of material while targeting the color of the test article. Then, 20 samples of the test article are added and the mix is reprocessed. Sorting efficiency of the test articles is compared to the baseline efficiency. Five passes through the color unit are used to develop repeat values for the test articles.

Note: Test results from one laboratory are sufficient since the evaluation is measured against that machine's own baseline.

Disclaimer: This document has been prepared by the Association of Plastic Recyclers as a service to the plastic industry to promote the most efficient use of the nation's plastic recycling infrastructure and to enhance the quality and quantity of recycled postconsumer plastic. The information in this document is offered without warranty of any kind, either expressed or implied, including WARRANTIES OF MERCHANTABILITY OR FITNESS FOR A PARTICULAR PURPOSE, which are expressly disclaimed. APR and its members accept no responsibility for any harm or damages arising from the use of or reliance upon this information by any party. Participation in the Recognition Program is purely voluntary and does not guarantee compliance with any U.S. law or regulation or that a package or plastic article incorporating the innovation is recyclable or will be recycled.

Reference Documents:

- Compression Practice:
<https://plasticsrecycling.org/images/Design-Guidance-Tests/APR-SORT-PR-01-compression-practice.pdf>
- APR Candidate Laboratories for Testing:
<https://plasticsrecycling.org/images/Design-Guidance-Tests/APR-candidate-test-labs.pdf>


Test/Method Summary and Flow Diagram

Safety Statement: APR Test and Practice documents do NOT CLAIM TO ADDRESS ALL OF THE SAFETY ISSUES, IF ANY, ASSOCIATED WITH THEIR USE. These Tests and Practices may require the use of electrically powered equipment, heated equipment and molten polymers, rotating motors and drive assemblies, hydraulic powered equipment, high pressure air, and laboratory chemicals. IT IS THE RESPONSIBILITY OF THE USER TO ESTABLISH AND FOLLOW APPROPRIATE SAFETY AND HEALTH PROCEDURES WHEN UNDERTAKING THESE TESTS AND PRACTICES THAT COMPLY WITH APPLICABLE FEDERAL, STATE AND LOCAL REGULATORY REQUIREMENTS. APR and its members accept no responsibility for any harm or damages arising from the use of or reliance of these Tests and Practice documents by any party.

The flow diagram below outlines the test process. First, the baseline sorting efficiency for the polymer in question is established by running a mix of known items through the color sorter and recording the sortation results. Then, 20 of the candidate articles are added to the mix and it is processed through the color sorter. This is repeated five times. The results of the baseline sorting efficiency and the candidate article sorting efficiency are then compared.

Note: The terms “test article” and “candidate article” are used synonymously throughout this document

Flow diagram:

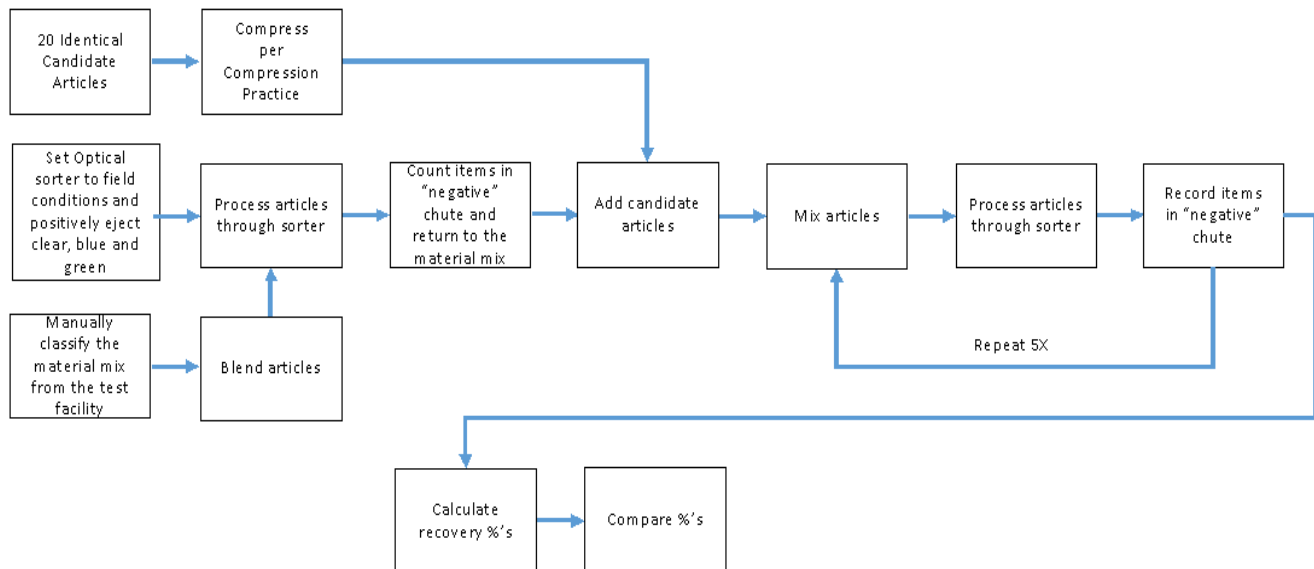

Equipment required:

1. Bottle compression device built per the instructions found on the [Compression Practice](#). Alternatively, a commercial horizontal or vertical baler may be used to compress articles for this test since color sorting occurs after the bottles have been baled. Many laboratories don't have balers on site so the compression protocol is acceptable.
2. Binary Color bottle sorter operating in representative (reflective or transmissive) mode of typical field equipment, with applicable feed belt and discharge chutes. This test is conducted on pilot plant scale color sortation equipment. Please refer to [APR Recognized Laboratories for Testing](#) for a list of potential test locations. Note that operating PET reclaimers are not normally prepared or experienced in this method, so a controlled laboratory environment is required. These businesses each maintain and operate pilot scale sorting equipment. There may be a service fee for pilot evaluations.

Materials required:

1. Twenty (20) identical candidate test articles provided by the test applicant. These articles should be fully decorated, i.e., with label, closures, etc. as they would be if placed in a curbside bin after consumer use. Note that these articles are empty whereas some residual product may remain in the articles found in the actual recycling stream. Sorting machines are generally programmed to minimize the effects of common amounts of residual product so this test does not consider residual product.
2. Mix of PET articles representing the proportions commonly processed through a PET recycling line. This mix should be of sufficient quantity to operate the trial sorting machine at 50% nameplate throughput or greater for at least one minute (a general rule of thumb for nameplate capacity is one ton per hour per meter of machine width, which equates to 34 pounds per minute, or approximately 733 bottles per minute, but this ratio is dependent on manufacturer). These articles are normally provided and maintained by the test lab, should be previously compressed through the actual collection system, and include labels and attachments. By weight percent the mix should consist of:
 - 83-86% by weight, clear and transparent light blue PET containers between 8 oz. and 2 liters, ensuring that at least 20 of each of the following are represented:
 - o clear single serve water
 - o transparent light blue single serve Dasani or similar color (Note: Dasani is chosen since it is generally regarded as the darkest blue accepted at a recycler)
 - o clear 2-liter carbonated soft drink
 - 10-13% by weight transparent green PET containers between 8 oz and 2 liters such as Mountain Dew or Sprite
 - 2-4% by weight colored PET containers between 8 oz and 2 liters, ensuring that at least 10 of each of the following colors are represented:
 - o Amber
 - o Opaque white
 - o Dark Blue

Method steps:

1. Take pictures of all articles for submission including:

- a. One candidate test article before compression
- b. All candidate test articles after compression (one collective picture)
- c. The mix of other articles (one collective picture)


2. Compress the candidate articles according to the APR [Compression Practice](#).

Alternatively, a horizontal or vertical ram baler may be used since color sorting in the recycling process is accomplished after the bottles have been baled.

Note: This is an extremely important step since compression helps flatten the articles, making them less likely to slide on the conveyor belt. Successful optical sorting requires articles to remain stable on the conveyor belt so the ejector can be timed with the sensor. Sorting tests performed on rounded items that are not compressed may have poor results.

3. Collect and classify the material mix. (It is anticipated that the testing lab maintains this mix in its facility for use as required and the classification has already been completed.)
- a. Complete the attached form in Annex #1, classifying the mix with the weight and count of each article type.
 - b. Ensure the mix is of sufficient size to feed the sorter at 50% rated throughput, or greater, for at least one minute. It is permissible and expected to adjust the usable width of the sorter to fall within these parameters.

WHY DOES THIS TEST POSITIVELY EJECT THE DESIRABLE COLORS?... BLACK.

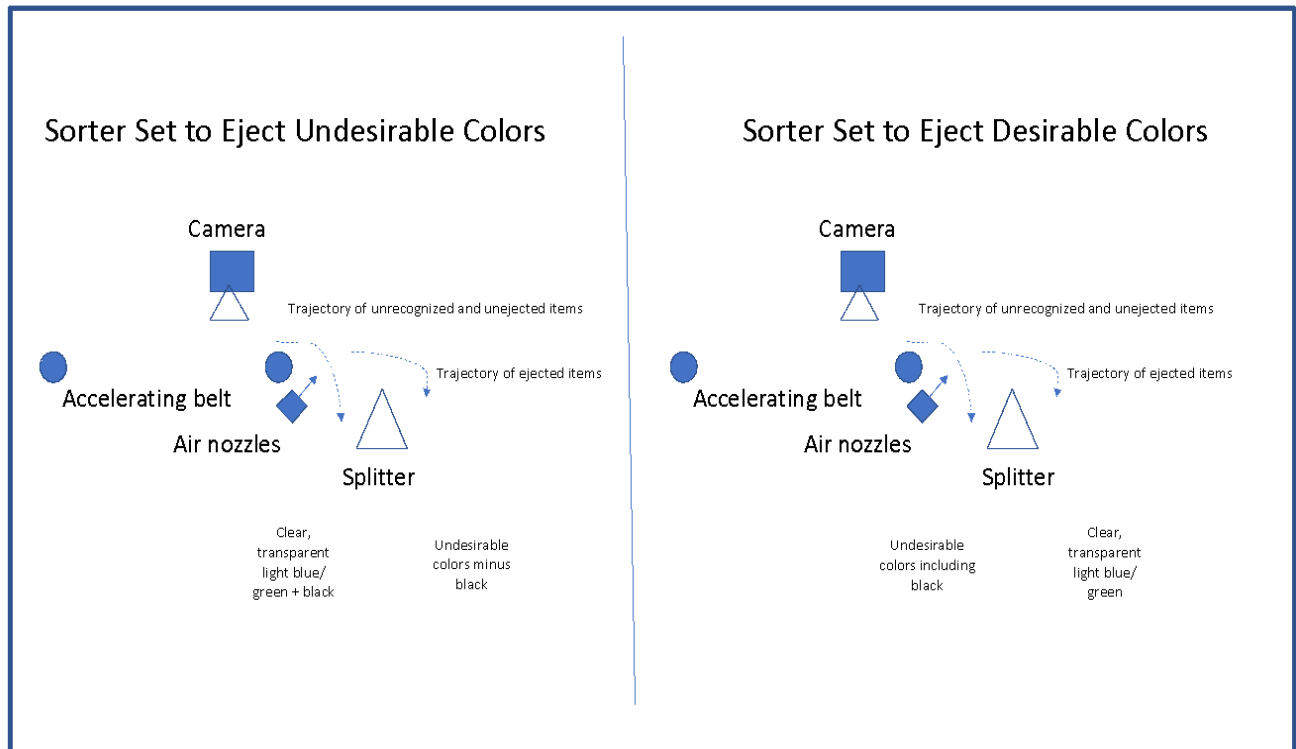

In the test described below, the desirable colors are ejected, as diagramed at right above. If the color sorter ejected the undesirable colors, as on left — the common color sort practice — black items would always pass this test. The desirable colors in the context of this test are containers that sort as clear or transparent light blue / green.

4. Establish the baseline:

- a. Using the manufacturer’s operating procedure and color only, set the sorter to positively sort a typical clear stream plus the typical green stream within a PET reclaimer into the same stream. **DO NOT USE THE TEST ARTICLE TO ADJUST THE SETTINGS.**

Note: The purpose of this test is to represent the performance of the machines in the field, not the capabilities of the latest machine version. Therefore, this test is not an appropriate brand-to-brand or machine-to-machine comparison.

- b. Blend the material mix without the candidate articles in a container so they are randomly mixed.
- c. Meter the mixed articles onto the accelerating belt (or vibratory feeder – depending on test facility) at a rate at least 50% of the sorters nameplate throughput.
- d. The mixture is carried by conveyor belt through the sortation equipment and sorted.

- e. Record the number and percent of the target polymer articles incorrectly sorted on the form below.
5. Test the candidate article:
- a. Combine both sorted streams to recreate the material mix.
 - b. Randomly place the candidate articles into the material mix. This can either be done by mixing them all in a bin or by placing the candidate articles one at a time onto the accelerating belt while the material mix is being processed.
 - c. Meter the mixed articles onto the accelerating belt (or vibratory feeder – depending on test facility) at a rate at least 50% of the sorters nameplate throughput.
 - d. Record the number of candidate articles positively sorted on the form below.
 - e. Repeat 5 times. Note, if a label dislodges from a candidate article at any time, replace that candidate article in the next repetition.

Measurements: For each run, record the count of the test articles in the un-ejected stream per the report form.

Report Form: Found in Annex 1

Assessment:

Variance = The difference between the sorting efficiency of the test polymer established in the baseline test, minus the sorting efficiency of the test article in aggregate of the following tests (see calculations in the report form and example).

Capture rate = The average percentage of test articles correctly sorted in the aggregate of the tests (see calculations in the report form and example).

If:

Variance is <=5%: The candidate article is most likely to be sorted correctly by the color sorter and the APR Design Guidance category for the design feature of “optical sorting potential” is preferred.

Variance is >5%: A higher than optimal percentage of the test articles will be missorted by the color sorter. The APR Design Guidance category for the design feature “color sorting potential” is detrimental.



Annexes:

1. **Report form: Evaluation of the Color Sorting Potential of a Clear PET Article with Label Coverage Greater than APR Design Guide Limits**
2. **Sample completed report form and calculations**

Table and Figures – None

Annex 1: Report Form

**Evaluation of the Color Sorting Potential of a
Clear PET Article with Label Coverage Greater than APR Design Guide Limits
Record Sheet - APR Test #**

BACKGROUND	
TESTING FACILITY	
TESTING FACILITY TECHNICIAN	
DATE	
CANDIDATE ARTICLE DESCRIPTION	Volume _____
	Color Clear
	Label Material _____
	Closure material _____
	Body material PET
	Brand/Description _____

MACHINERY
NAMEPLATE THROUGHPUT FOR THE WIDTH USED -lbs/hr _____
WEIGHT OF MATERIAL REQUIRED FOR 50% RATED THROUGHPUT FOR 1 MINUTE: - lbs _____

MATERIAL MIX			
Material	Target % by weight	Actual weight	Count
Clear & Transparent lgt blue PET containers	83-86%		
Transparent green PET containers	10-13%		
Colored PET containers	2-4%		
Total			
			% Of material required for 1 minute run

BASELINE TEST	
# of clear, transparent light blue and transparent green articles in the negative sort bin (incorrectly sorted)	_____
% of clear, transparent light blue and transparent green articles incorrectly sorted	_____
Baseline capture rate: (100% - % incorrectly sorted)	_____

CANDIDATE ARTICLE TESTS						
	RUN 1	RUN 2	RUN 3	RUN 4	RUN 5	TOTAL
# of test articles incorrect						
% of test articles incorrect						
Test capture rate (100% - total incorrectly sorted)						

VARIANCE CALCULATION	
Baseline capture rate - Test Capture rate	
	variance _____

ASSESSMENT			
Variance		Applicable APR Recyclability Category for "NIR Sorting Potential" (see category definitions In APR Design Guide for Plastics Recyclability Home Page)	Check Applicable Box
< = 5%		APR Design Guide Preferred	
> 5%		Detrimental to Recycling	

Testing Facility Technician Signature _____

Comments: What features cause negative results?, What could be done to improve sorting? etc.

These results are not to be misinterpreted or misused to judge the performance of individual machine manufacturers.



Annex 2: Sample Completed Form and Calculations

Evaluation of the Color Sorting Potential of a
Clear PET Article with Label Coverage Greater than APR Design Guide Limits
Record Sheet - APR Test #

BACKGROUND	
TESTING FACILITY	DOES SORTING
TESTING FACILITY TECHNICIAN	JANE DOE
DATE	SEP 24, 2020
CANDIDATE ARTICLE DESCRIPTION	Volume 600 ml
	Color Clear
	Label Material PP
	Closure material PP
	Body material PET
	Brand/Description ACME JUICE

MACHINERY	
NAMEPLATE THROUGHPUT FOR THE WIDTH USED -lbs/hr	2000
WEIGHT OF MATERIAL REQUIRED FOR 50% RATED THROUGHPUT FOR 1 MINUTE: - lbs	17 (2000/60/2)

MATERIAL MIX			
Material	Target % by weight	Actual weight	Count
Clear & Transparent lgt blue PET containers	83-86%	25.5	459
Transparent green PET containers	10-13%	3.3	59
Colored PET containers	2-4%	1.2	30
	Total	30	
		176%	% Of material required for 1 minute run
	30/17		




BASELINE TEST	
# of clear, transparent light blue and transparent green articles in the negative sort bin (incorrectly sorted)	20
% of clear, transparent light blue and transparent green articles incorrectly sorted	$\left(\frac{20}{(459+59)}\right) \times 100 = 3.9\%$
Baseline capture rate: (100% - % incorrectly sorted)	$100 - 3.9 = 96.1$

CANDIDATE ARTICLE TESTS						
	RUN 1	RUN 2	RUN 3	RUN 4	RUN 5	TOTAL
# of test articles incorrect	1	2	1	2	0	6
% of test articles incorrect	5%	10%	5%	10%	0%	94%
Test capture rate (100% - total % incorrectly sorted)						$100 - 6 = 94\%$

VARIANCE CALCULATION	
Baseline capture rate - Test Capture rate	$96.1 - 94 = \text{variance } 2.1\%$

ASSESSMENT			
Variance		Applicable APR Recyclability Category for "NIR Sorting Potential" (see category definitions In APR Design Guide for Plastics Recyclability Home Page)	Check Applicable Box
<= 5%	2.1	APR Design Guide Preferred	✓
> 5%		Detrimental to Recycling	

Testing Facility Technician Signature 

Comments: What features cause negative results?, What could be done to improve sorting? etc.

These results are not to be misinterpreted or misused to judge the performance of individual machine manufacturers.

DOCUMENT VERSION HISTORY

Version	Publication Date	Revision Notes
1	May 27, 2021	