

## Benchmark Evaluation for Clear PET Articles with Labels and Closures

Document number – PET-B-02

Creation or Revision Date: April 11, 2019

### Introduction – Scope, significance and use

This is a laboratory scale evaluation that can be used to assess the compatibility of PET packaging design features such as labels, closures, dispensers and attachments with some of the common commercial scale recycling process steps. This test is only applicable to clear PET articles. Product developers, as well as those who specify products, can employ this test to maintain and improve the quality and productivity of PET recycling.

The evaluation is conducted with molded articles made from clear PET and employs the packaging design feature of interest, (the “innovation material”). Clear PET refers to natural color PET with no colorants added at the molding process. Molded articles are most often expected to be PET packages: injection stretch blow molded containers, extrusion blow molded containers, or thermoformed sheet products; but may include any article that would be sorted as clear PET in the collection and sorting system.

This test is used to understand how molded articles behave in the wash, float/sink and elutriation steps. The test is also valuable for understanding any impact of resin drying and melt heat history during injection molding on the formation of color, haze or inclusions in molded PET.

This test does not include an assessment of flake extrusion and melt filtration that is a necessary component of the Critical Guidance Protocol for PET Articles with Labels and Closures. This test does not consider the effects of package design on sortation in a MRF or reclaiming process.

**Disclaimer:** *This document has been prepared by the Association of Plastic Recyclers as a service to the plastic industry to promote the most efficient use of the nation’s plastic recycling infrastructure and to enhance the quality and quantity of recycled postconsumer plastic. The information in this document is offered without warranty of any kind, either expressed or implied, including WARRANTIES OF MERCHANTABILITY OR FITNESS FOR A PARTICULAR PURPOSE, which are expressly disclaimed. APR and its members accept no responsibility for any harm or damages arising from the use of or reliance upon this information by any party. Participation in the Recognition Program is purely voluntary and does not guarantee compliance with any U.S. law or regulation or that a package or plastic article incorporating the innovation is recyclable or will be recycled.*

## Method summary and flow diagram

Molded articles used for control can either be made from a named control resin or by qualifying a resin for control using the PET Heat History and Color Evaluation Test.

Innovation articles are created according to the “Preparation of PET Articles for Evaluation” Practice which explains how to create articles for evaluation that include labels, closures or attachments. Innovation articles are usually mixed with control articles that do not have the design feature of interest; this mix is granulated to make a flake blend sample used in the evaluation.

The evaluation involves:

- Granulation, wash and elutriation of each set of control bottles and articles which employ the innovation.
- Injection molding plaques directly from washed flake made from each material.

Inks and adhesives can impact the costs of managing a wash system and waste disposal. Therefore, if inks or adhesives are observed in the wash water it is recommended that the Wash Water Evaluation for articles with labels and direct printing be performed.

This procedure offers some optional steps that can be valuable in certain investigations. Examples are:

- The oven bake test for flake, and flake color evaluation to evaluate for contamination before injection molding of flake.
- A materials balance to confirm that materials are recovered as expected as sinking or floating solids.

A flow diagram in Appendix I illustrates the testing steps.

## Reference Documents

The following documents are referenced in this Critical Guidance Protocol:

APR PET Standard Laboratory Practices, PET-P-00

APR PET Screening Test Methods:

PET Package Materials Balance, PET-S-04

Labels for PET - Wash Water Evaluation, PET-S-01

PET Flake Clumping Evaluation, PET-S-08

PET Flake Oven Bake Evaluation, PET-S-10

Measurement of PET Flake or Pellet Discoloration, PET-S-02

Evaluation of PET Plaques for Color, Haze and Inclusions, PET-S-09

ASTM Methods

ASTM D4603-18 Standard Test Method for Determining Inherent Viscosity of Poly(Ethylene Terephthalate) (PET) by Glass Capillary Viscometer

ASTM D1238 – 13 Standard Test Method for Melt Flow Rates of Thermoplastics by Extrusion Plastometer

## Method steps

**Safety Statement:** *APR Test and Practice documents do NOT CLAIM TO ADDRESS ALL OF THE SAFETY ISSUES, IF ANY, ASSOCIATED WITH THEIR USE. These Tests and Practices may require the use of electrically powered equipment, heated equipment and molten polymers, rotating motors and drive assemblies, hydraulic powered equipment, high pressure air, and laboratory chemicals. IT IS THE RESPONSIBILITY OF THE USER TO ESTABLISH AND FOLLOW APPROPRIATE SAFETY AND HEALTH PROCEDURES WHEN UNDERTAKING THESE TESTS AND PRACTICES THAT COMPLY WITH APPLICABLE FEDERAL, STATE AND LOCAL REGULATORY REQUIREMENTS. APR and its members accept no responsibility for any harm or damages arising from the use of or reliance of these Tests and Practice documents by any party.*

The following steps are taken with reference to the PET Practices, PET-P-01 through PET-P-08 (included in document PET-P-00) and the flow diagram shown in Appendix I:

1. Secure molded control articles.
2. Prepare these innovation articles according to the Practice for Preparation of PET Articles for Evaluation.
3. Create a blend of control and innovation articles as described in the Preparation of PET Articles for Evaluation
4. Separately grind control articles to create flake sample A and then grind the blend of control and innovation articles to create flake sample B.
5. Separately wash flake samples A and B.
6. When flake sample B contains labels, adhesives or printed surfaces, retain a sample of wash water created from washing flake sample B for evaluation.
7. Elutriate flake samples A and B.
8. If necessary, crystallize flake samples A and B prior to desiccant drying to prevent any sticking in the drier.
9. If necessary to allow feeding to the injection molding unit, grind flake samples A and B to a finer flake size.
10. Desiccant dry and injection mold plaques from each of elutriated flake samples A and B to create amorphous plaques A and B.

## Measurements, report, and guidance values

### Wash and elutriation evaluations

Property	Test method	APR Guidance Preferred values	Additional Guidance
<u>Required values</u>			
Clumping test with flake sample B	PET Flake Clumping Evaluation, PET-S-08	<1 wt% retention on screen for each evaluation	
Wash water evaluation report	Labels for PET - Wash Water Evaluation, PET-S-01		Required only for label and direct printing evaluations
<u>Optional values</u>			
Flake bake test	PET Flake Oven Bake Evaluation, PET-S-10		Can reveal contamination before later evaluations
Flake color	Measurement of PET Flake or Pellet Discoloration, PET-S-02		Can reveal contamination before later evaluations
Materials balance	PET Package Materials Balance, PET-S-04		Can reveal contamination before later evaluations


### Evaluation of molded plaques

IV loss - The table below calls for reporting the IV loss when samples are injection molded into plaques. The following steps are used to report this value using samples A and B for illustration:

- Measure the IV of flake created from control articles as well as from innovation articles.
- Calculate the arithmetic mean IV of flake blend sample B and employ the mean value as the IV of the blend of control and innovation.
- Measure the IV of the resulting plaques for each blend after molding.
- Measure the IV loss for sample A with molding and call that value A'. This is the IV loss for the control.
- Measure the IV loss for Sample B with molding and call that value B'. This is the IV loss for the 50:50 blend of innovation and control.

<b>Property</b>	<b>Test method</b>	<b>APR Guidance Preferred values</b>
<u>Required values</u>		
IV loss when molding plaques	ASTM D 4603 solution IV with phenol/tetrachlorethane at 30 <sup>o</sup> or ASTM D1238 – 13 method B	Difference in A' and B' is 0.025 dg/l or less
L value of plaques B	Plaque Color Measurement, PET-S-09	>82
a* value of plaques A and B	Plaque Color Measurement	Less than 1.5 units difference between plaques A and B
b* value of plaques A and B	Plaque Color Measurement	Less than 1.5 units difference between A and B
% haze of plaques A and B	Plaque Color Measurement	Control not to exceed 9% value, and test not to exceed more than 10% units greater than control.
Inclusions and specks in plaques T5	Plaque Color Measurement	If A = 0; B is 2 or less If A = 1; B is 4 or less If A = 2; B is 6 or less

## Appendix I Benchmark Flow Diagram Natural PET Articles with Labels and Closures

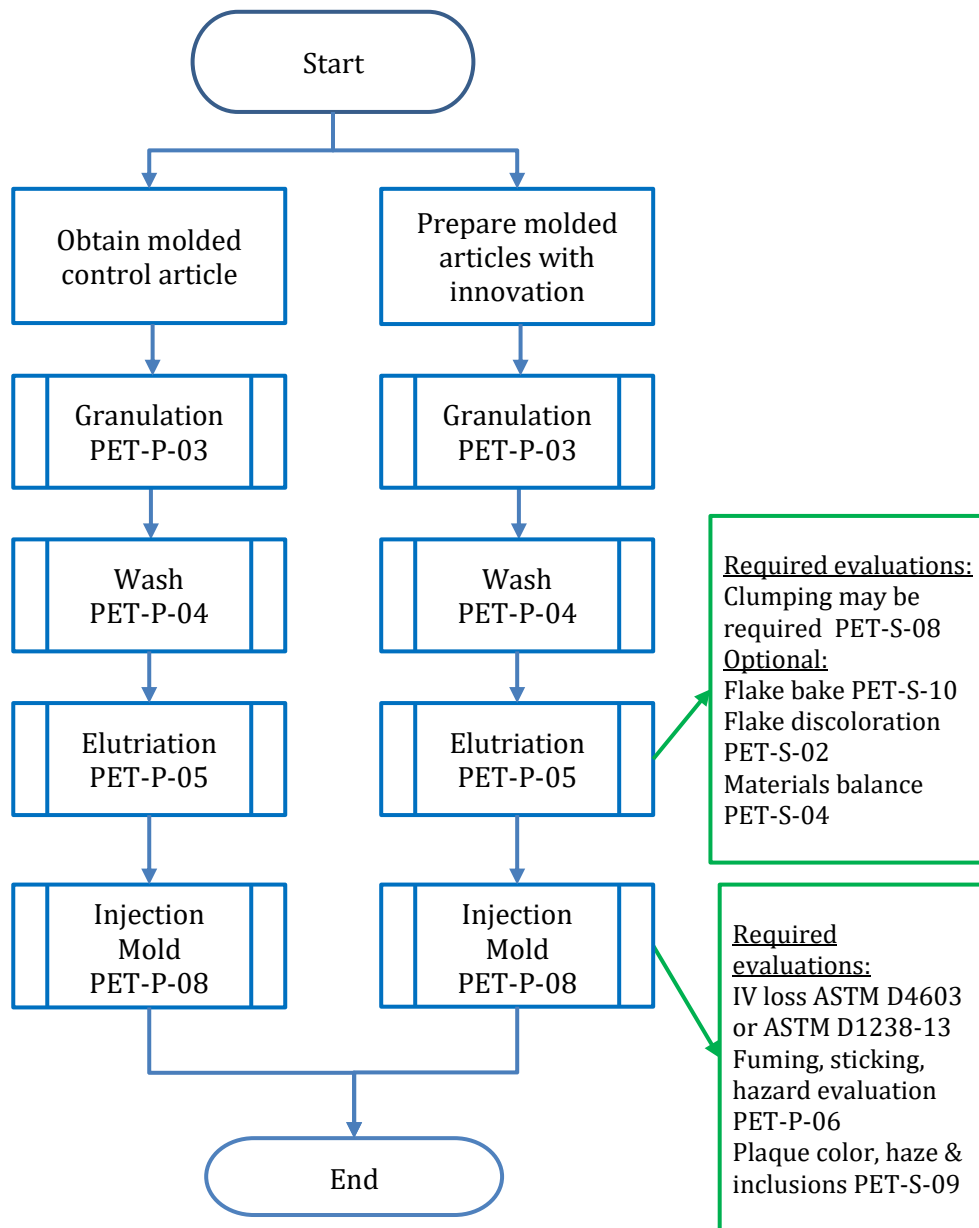

## DOCUMENT VERSION HISTORY

<b>Version</b>	<b>Publication Date</b>	<b>Revision notes</b>
1	November 16, 2018	
2	April 11, 2019	Revised Haze Guidance Preferred Values as approved by PTC in March 2019